


Creating Material Change



C-TUFF™ CT-8
Processing Guide

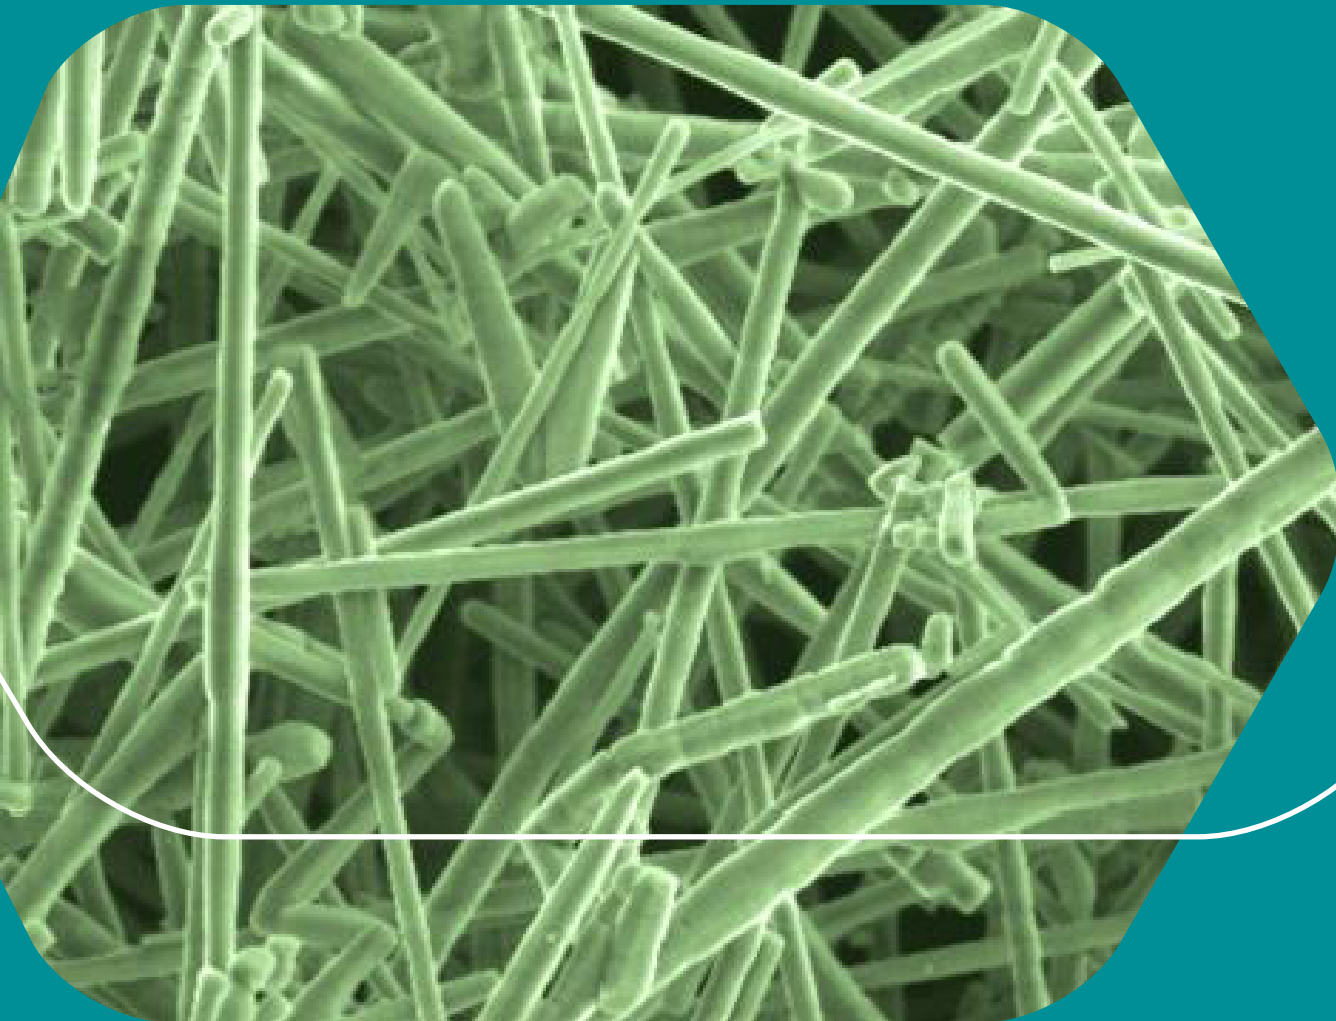

Innovation underpins everything we do

www.haydale-technologies.com



HaydaleGraphene



CT-8 Firing Cycle Guidelines

C-TUFF™ CT-8 is supplied with a binder and can be debinded under atmospheric conditions at temperatures of 475-500°C. It must be fired under inert atmosphere. The following should be considered guidelines for processing C-TUFF™ CT-8. They may need to be adjusted based on equipment, part dimensions, and application.

Segment	Time (hh:mm)	Temperature (°C)	Rate (°C/min)
1	0:10	50	3.0
2	0:15	50	Hold
3	2:40	600	3.5
4	2:15	1000	3.0
5	3:00	1500	2.75
6	0:20	1500	Hold
7	0:30	1575	2.5
8	0:30 (smaller parts) 0:90 (larger parts)	1575	Hold
9	-	20	-
	9:10 (smaller parts) 10:10 (larger parts) Plus cooling time		

Firing Cycle Explanation

Segment	Description
1	Heat to 50°C at 3.0°C/minute
2	Hold temperature at 50°C for 15 minutes
3	Heat to 600°C at 3.5°C/minute
4	Heat to 1000°C at 3.0°C/minute
5	Heat to 1500°C at 2.75°C/minute
6	Hold temperature at 1500°C for 20 minutes
7	Heat to 1575°C at 2.5°C/minute
8	Hold temperature at 1575°C for 30-90 minutes, depending on size and geometry of part.
9	Turn heat off and cool down

The content supplied in this processing guide ("Information") supersedes all previous versions supplied. Version 1, October 2019

The Information should be used solely as guidance for the safe handling, storage, processing and/or use of the Product and is only typical of the methods described. The Haydale Group (Haydale Group means Haydale Technologies Inc., as a subsidiary of Haydale Graphene Industries plc., and any subsidiary or holding company from time to time and any subsidiary from time to time of any holding company of Haydale Limited) gives no express or implied warranty or guarantee or representation as to the behaviour of the Product described herein during any handling or storage or processing or use of the Product. To the extent permissible by law the Haydale Group shall under no circumstances whatever be liable whether in contract, tort (including negligence), breach of statutory duty, or otherwise, for any damage, including loss of profit, or any indirect or consequential loss arising under or in connection with any handling or storage or processing or use of the Product.



Contact us: info@haydale.com